



Designation: D1384 – 24

## Standard Test Method for Corrosion Test for Engine Coolants in Glassware<sup>1</sup>

This standard is issued under the fixed designation D1384; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon ( $\epsilon$ ) indicates an editorial change since the last revision or reappraisal.

### 1. Scope

1.1 This test method covers a simple beaker-type procedure for evaluating the effects of engine coolants on metal specimens under controlled laboratory conditions (see [Appendix X1](#)).

NOTE 1—For more information on engine coolants, see (Refs [1-8](#)).<sup>2</sup>

1.2 The values stated in SI units are to be regarded as standard. The values given in parentheses after SI units are provided for information only and are not considered standard.

1.3 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.* Specific hazard statements are given in [11.1.7.2](#), [11.1.7.3](#), and [11.1.7.4](#).

1.4 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

### 2. Referenced Documents

#### 2.1 ASTM Standards:<sup>3</sup>

[B32 Specification for Solder Metal](#)

[B36/B36M Specification for Brass Plate, Sheet, Strip, And Rolled Bar](#)

[D1176 Practice for Sampling and Preparing Aqueous Solutions of Engine Coolants or Antirusts for Testing Purposes](#)

[D4725 Terminology for Engine Coolants and Related Fluids](#)

[E1 Specification for ASTM Liquid-in-Glass Thermometers](#)

<sup>1</sup> This test method is under the jurisdiction of ASTM Committee [D15](#) on Engine Coolants and Related Fluids and is the direct responsibility of Subcommittee [D15.06](#) on Glassware Performance Tests.

Current edition approved Jan. 1, 2024. Published February 2024. Originally approved in 1955. Last previous edition approved in 2019 as D1384 – 05 (2019). DOI: 10.1520/D1384-24.

<sup>2</sup> The boldface numbers in parentheses refer to the list of references at the end of this standard.

<sup>3</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

[E177 Practice for Use of the Terms Precision and Bias in ASTM Test Methods](#)

[E178 Practice for Dealing With Outlying Observations](#)

[E230 Specification for Temperature-Electromotive Force \(emf\) Tables for Standardized Thermocouples](#)

[E691 Practice for Conducting an Interlaboratory Study to Determine the Precision of a Test Method](#)

[G31 Guide for Laboratory Immersion Corrosion Testing of Metals](#)

#### 2.2 ASTM Adjuncts:

All-glass apparatus for corrosion test (2 drawings)<sup>4</sup>

### 3. Terminology

3.1 *Definitions*—For definitions of general terms used in D15 standards, refer to Terminology [D4725](#).

#### 3.2 Abbreviations:

3.2.1 *PTFE, n*—Polytetrafluoroethylene

### 4. Summary of Test Method

4.1 In this test method, specimens of metals typical of those present in engine cooling systems are totally immersed in aerated engine coolant solutions for 336 h at 88 °C (190 °F). The corrosion-inhibitive properties of the test solution are evaluated on the basis of the weight changes incurred by the specimens. Each test is run in triplicate, and the average weight change is determined for each metal. A single test may occasionally be completely out of line (see [12.2](#)).

### 5. Significance and Use

5.1 This test method will generally distinguish between coolants that are definitely deleterious from the corrosion standpoint and those that are suitable for further evaluation. However, the results of this test method cannot stand alone as evidence of satisfactory corrosion inhibition. The actual service value of an engine coolant formulation can be determined only by more comprehensive bench, dynamometer, and field tests.

### 6. Apparatus

6.1 *Container*—A 1000 mL, tall-form, spoutless beaker, made of heat-resistant glass, for containing the engine coolant

<sup>4</sup> Details available from: ASTM International Headquarters. Order Adjunct No. [ADJD1384](#). Original adjunct produced in (1980).

solution and test specimens. The beaker shall be tightly closed with a No. 15 rubber stopper, having drill holes to accommodate a water condenser, an aerator tube, and a thermometer as shown in Fig. 1. Optionally, an all-glass apparatus may be used (Fig. 2).

6.2 *Condenser*—A water condenser of the reflux, glass-tube type, having a 400 mm (16 in.) condenser jacket.

6.3 *Aerator Tube*—A gas-dispersion tube, porosity size 40  $\mu\text{m}$  to 60  $\mu\text{m}$  to ensure continuous aeration without plugging. Optionally, a capillary tip bleed tube with a 7 mm (0.28 in.) bore and 280 mm (11.2 in.) length may be used when consistent early plugging of gas dispersion tubes occurs.

6.4 *Temperature Measuring Instrument (Environmentally Safe Thermometer or Thermocouple)*—An ASTM Partial Immersion Temperature Measuring Instrument having a range from  $-20^{\circ}\text{C}$  to  $150^{\circ}\text{C}$  ( $0^{\circ}\text{F}$  to  $302^{\circ}\text{F}$ ) and conforming to the requirements for Thermometer 1C (1F), as prescribed in Specification E1 or Thermocouple as summarized in Specification E230.

6.5 *Heater*—A constant-temperature bath containing a high-boiling liquid or another suitable heating device that is capable of giving continuous service with the specified temperature control.

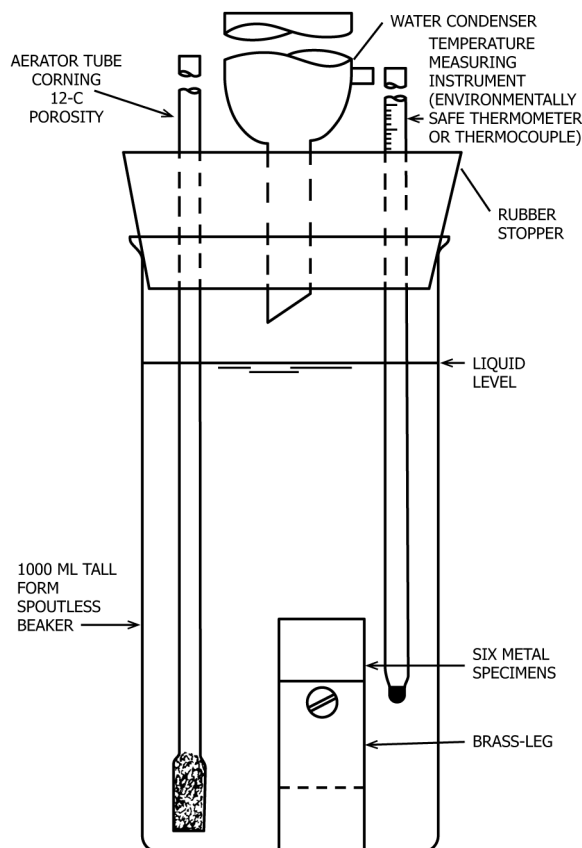


FIG. 1 Metal Specimens and Equipment for the 336 h Corrosion Test

## 7. Metal Test Specimens

7.1 *Type*—Either one or both of the following metal test specimen bundles, representative of cooling system metals, may be used as agreed between customer and supplier (see Note 2):

NOTE 2—The specimens prescribed in this test method have been accepted by automobile manufacturers, but their composition may not be the same as that of alloys currently used for engine cooling system components. Therefore, specimens other than those designated in this test method may be used by mutual agreement of the parties involved.

NOTE 3—When assembling the test bundle, sizes are stated in SI units, adjustment to these units may be made to accommodate US customary units, that is, 51 mm or 2 in.

7.1.1 Test Specimen bundle with copper and copper alloy (“conventional bundle”).

7.1.1.1 *Steel*, UNS G10200 (SAE 1020),<sup>5</sup> cut from 1.59 mm ( $\frac{1}{16}$  in.) cold-rolled sheet stock to size 50.8 mm by 25.4 mm (2 in. by 1 in.). Chemical composition of the carbon steel is as follows: carbon, 0.17 % to 0.23 %; manganese, 0.30 % to 0.60 %; phosphorus, 0.040 % maximum; sulfur, 0.050 % maximum.

7.1.1.2 *Copper*, conforming to UNS C11000 (SAE CA110)<sup>5</sup> or UNS C11300 (SAE CA113).<sup>5</sup> Cold-rolled, cut from 1.59 mm ( $\frac{1}{16}$  in.) sheet stock to size 50.8 mm by 25.4 mm (2 in. by 1 in.).

7.1.1.3 *Brass*, conforming to Alloy UNS C26000 (SAE CA 260).<sup>6</sup> Half-hard, cut from 1.59 mm ( $\frac{1}{16}$  in.) sheet stock to size 50.8 mm by 25.4 mm (2 in. by 1 in.).

7.1.1.4 *Solder*—A brass specimen as described in 7.1.1.3, coated with solder conforming to Alloy Grade 30A (SAE 3A) of Specification B32.<sup>6</sup> Solder-coated specimens may be prepared by the procedure given in Annex A1. A solid solder specimen cut from 1.59 mm ( $\frac{1}{16}$  in.) sheet stock of Alloy Grade 30A (SAE 3A) to size 50.8 mm by 25.4 mm (2 by 1 in.) may be used subject to mutual agreement of the parties involved. The use of a solid solder specimen must be reported along with the metal specimen weight loss results.

(1) When agreed upon between the supplier and the purchaser of engine coolants, the standard solder specimen may be replaced with one having a different alloy composition than standard Alloy Grade 30A or 30B. Use of specimens other than standard Alloy Grade 30A or 30B shall be noted in the test report.

NOTE 4—Where non-standard alloy is used, the standard flux shown in A1.1.5 may not be satisfactory. A low corrosive flux may be required.

7.1.1.5 *Cast Aluminum*, conforming to Alloy UNS A23190 (SAE 329).<sup>5</sup> Specimen size, 50.8 mm by 25.4 mm by 3.18 mm (2 in. by 1 in. by  $\frac{1}{8}$  in.).

7.1.1.6 *Cast Iron*, conforming to Alloy UNS F10007 (SAE G3500).<sup>5</sup> Specimen size, 50.8 mm by 25.4 mm by 3.18 mm (2 in. by 1 in. by  $\frac{1}{8}$  in.).

7.1.2 Test Specimen bundle with no copper, copper alloy, or steel test specimen (“aluminum bundle”).

<sup>5</sup> UNIFIED numbering system for metals and alloys, SAE-ASTM, July 1995.

<sup>6</sup> Round-robin evaluation of coated solder report is available from ASTM Headquarters. Request RR:D15-0132.