



Designation: D4027 – 98 (Reapproved 2019)

Standard Test Method for Measuring Shear Properties of Structural Adhesives by the Modified-Rail Test¹

This standard is issued under the fixed designation D4027; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ϵ) indicates an editorial change since the last revision or reapproval.

1. Scope

1.1 This test method describes equipment and procedures to measure the shear modulus and shear strength of adhesive layers between rigid adherends. The equipment may also be used for determining the adhesive's shear creep compliance, the effects of strain history such as cyclic loading upon shear properties, and a failure criteria for biaxial stress conditions such as shear plus tension and shear plus compression.²

1.2 High-density wood shall be the preferred substrate. The practical upper limit on the shear modulus that can be measured is determined by the shear modulus of the adherends and by the strain measuring device. Thus, the practical limit of adhesive shear modulus that can be measured using high-density wood adherends is about 690 MPa (1×10^5 psi).

NOTE 1—Wood-base composites, metal, plastic, reinforced plastics, and other common construction materials may also be used for adherends.

1.3 The range of specimen dimensions that can be tested are: width 1.59 to 12.70 mm (0.0625 to 0.500 in.), length 102 to 203 mm (4 to 8 in.), and adherend thickness 13 to 25 mm (0.50 to 1.00 in.). The standard specimen dimensions shall be: width 3.18 mm (0.125 in.), length 203 mm (8 in.), and adherend thickness 19 mm (0.75 in.). Bondline thicknesses from 0.15 to 3.18 mm (0.006 to 0.125 in.) may be tested.

1.4 The values stated in SI units are to be regarded as standard. The values given in parentheses after SI units are provided for information only and are not considered standard.

1.5 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

¹ This test method is under the jurisdiction of ASTM Committee D14 on Adhesives and is the direct responsibility of Subcommittee D14.70 on Construction Adhesives.

Current edition approved March 1, 2019. Published March 2019. Originally approved in 1981. Last previous edition approved in 2011 as D4027 – 98 (2011). DOI: 10.1520/D4027-98R19.

² Kreuger, G. P., "Tests for the Shear Properties of Adhesives in Adherend-Adhesive Assemblies," Unpublished report. Michigan Technological Institute, Houghton, MI.

1.6 *This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

2. Referenced Documents

2.1 *ASTM Standards:*³

D905 Test Method for Strength Properties of Adhesive Bonds in Shear by Compression Loading

D907 Terminology of Adhesives

D4442 Test Methods for Direct Moisture Content Measurement of Wood and Wood-Based Materials

E83 Practice for Verification and Classification of Extensometer Systems

E229 Test Method for Shear Strength and Shear Modulus of Structural Adhesives (Withdrawn 2003)⁴

3. Terminology

3.1 *Definitions:*

3.1.1 Many terms in this test method are defined in Terminology D907.

3.1.2 *shear modulus, n*—the ratio of shear stress to corresponding shear strain below the proportional limit. (Compare *secant modulus*.)

3.1.2.1 *Discussion*—The term shear modulus is generally reserved for materials that exhibit linear elastic behavior over most of their stress-strain diagram. Many adhesives exhibit curvilinear or nonelastic behavior, or both, in which case some other term, such as secant modulus, may be substituted.

3.1.3 *shear strain, n*—the tangent of the angular change, due to force between two lines originally perpendicular to each other through a point in the body.

3.1.3.1 *Discussion*—Shear strain equals adherend slip/adhesive layer thickness.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

⁴ The last approved version of this historical standard is referenced on www.astm.org.

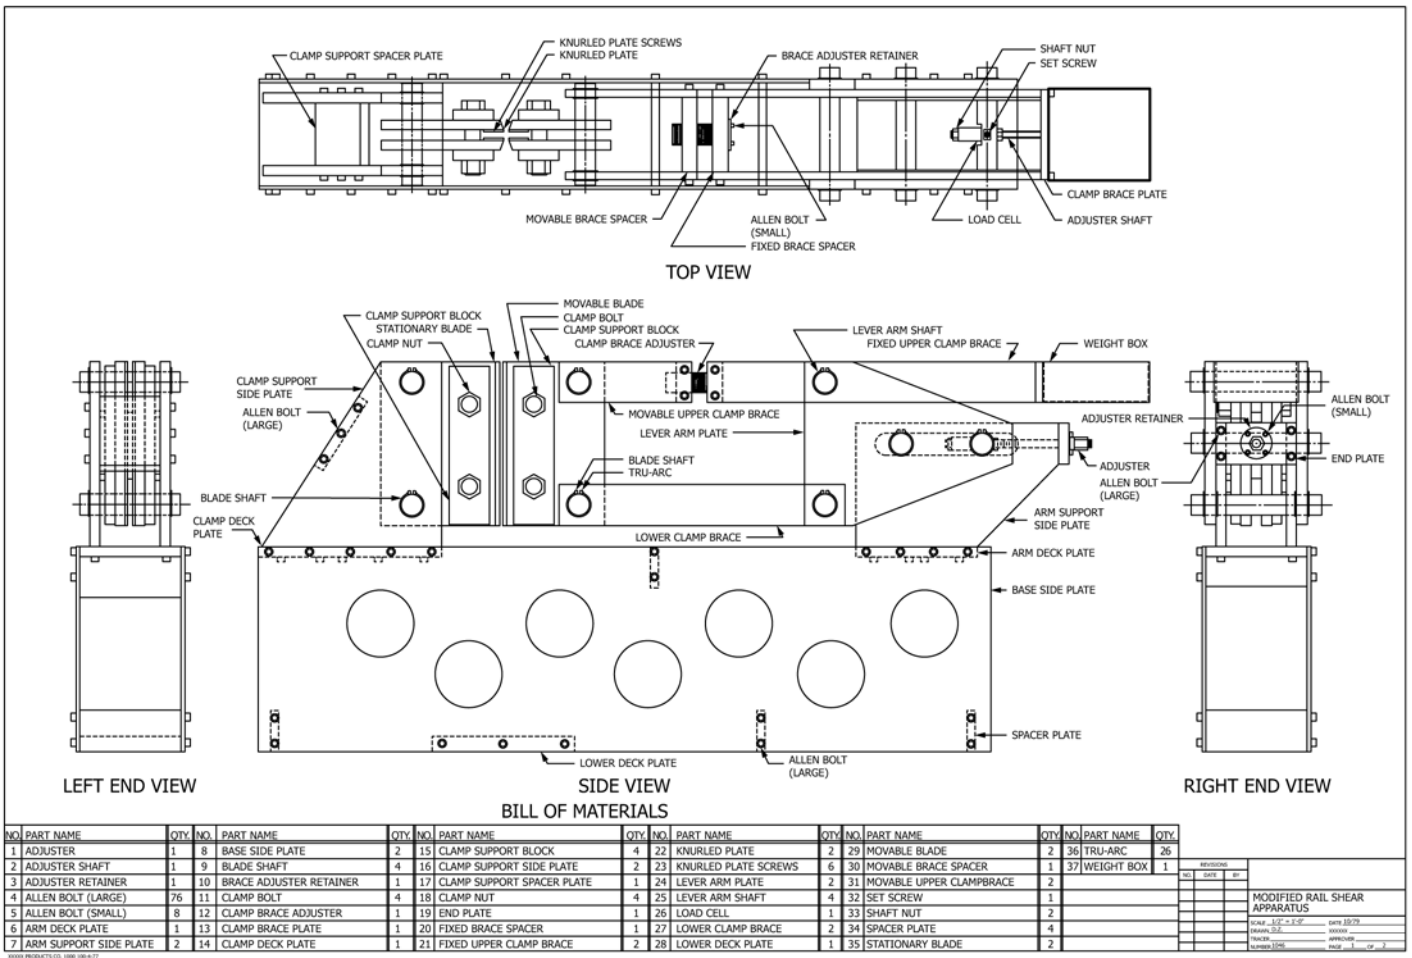


FIG. 1 Top, Side, and End Views of the Modified-Rail Shear Apparatus

3.1.4 *shear strength, n* —in an adhesive joint, the maximum average stress when a force is applied parallel to the joint.

3.1.4.1 *Discussion*—In most adhesive test methods, the shear strength is actually the maximum average stress at failure of the specimen, not necessarily the true maximum stress in the material.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 *load, n* —the force applied to the specimen at any given time.

3.2.2 *load-slip diagram, n* —a diagram in which corresponding values of load and slip are plotted against each other. Values of load are usually plotted as ordinates and values of slip as abscissas.

3.2.3 *normal stress, n* —the stress component perpendicular to a plane on which the forces act, that is, perpendicular to the plane of the bondline.

3.2.4 *proportional limit, n* —the maximum stress that a material is capable of sustaining without significant deviation from proportionality of stress to strain.

3.2.5 *secant modulus, n* —the slope of the secant drawn from the origin to any specified point on the stress-strain curve.

3.2.5.1 *Discussion*—Modulus is expressed in force per unit area (megapascals, pounds-force per square inch, etc.).

3.2.6 *shear stress, n* —the stress component tangential to the plane on which the forces act, that is, in the plane of the bondline.

3.2.7 *slip, n* —the relative collinear displacement of the adherends on either side of the adhesive layer in the direction of the applied load.

3.2.7.1 *Discussion*—This term differs from that of the stress-strain diagram in that load and slip are not divided by bond area and bond thickness (the constants that convert load to stress and slip to strain). In actual practice, stress-strain information is generally collected in the form of a load-slip diagram for ease in plotting.

3.2.8 *stress-strain diagram, n* —a diagram in which corresponding values of stress and strain are plotted against each other. Values of stress are usually plotted as ordinates (vertically) and values of strain as abscissas (horizontally).

4. Summary of Test Method

4.1 Shear force is applied to the adhesive through the adherends by a modified-rail shear tool such as shown in Fig. 1. The adherends are firmly clamped between two pairs of rigid rails as shown in Fig. 2. One pair is fixed and the other is movable. The rigid rails limit undesired adherend deformation during testing. The pair of movable rails is fixed to two