



Designation: F2648/F2648M – 23

# Standard Specification for 50 mm to 1500 mm [2 in. to 60 in.] Annular Corrugated Profile Wall Polyethylene (PE) Pipe and Fittings for Land Drainage Applications<sup>1</sup>

This standard is issued under the fixed designation F2648/F2648M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reapproval. A superscript epsilon (ε) indicates an editorial change since the last revision or reapproval.

## 1. Scope\*

1.1 This specification covers requirements and test methods for annular corrugated profile wall polyethylene pipe and fittings with an interior liner. The inside diameters covered are 50 mm to 1500 mm [2 in. to 60 in.].

1.2 The requirements of this specification are intended to provide non-pressure (gravity flow) pipe and fittings for underground use for subsurface and land drainage systems, which do not operate under surcharge pressure heads.

NOTE 1—Pipe and fittings produced in accordance with this specification are to be installed in compliance with Practice D2321 or Practice F449 based on diameter limitations within the respective standards.

NOTE 2—Subsurface and land drainage systems pertain principally to non-municipal or private facilities for water table control, storm drainage and agricultural drainage applications. The products supplied under this specification are not intended for any sanitary sewer or municipal storm sewer applications.

1.3 This specification covers pipe and fittings with an interior liner using an annular exterior corrugated profile (Fig. 1).

1.4 This specification permits the use of recycled materials for pipe in accordance with the requirements in Section 5.

1.5 *Units*—The values stated in either SI units or inch-pound units are to be regarded separately as standard. The values stated in each system are not necessarily exact equivalents; therefore, to ensure conformance with the standard, each system shall be used independently of the other, and values from the two systems shall not be combined.

1.6 *This standard does not purport to address all of the safety concerns, if any, associated with its use. It is the responsibility of the user of this standard to establish appropriate safety, health, and environmental practices and determine the applicability of regulatory limitations prior to use.*

<sup>1</sup> This specification is under the jurisdiction of ASTM Committee F17 on Plastic Piping Systems and is the direct responsibility of Subcommittee F17.65 on Land Drainage.

Current edition approved May 1, 2023. Published May 2023. Originally approved in 2007. Last previous edition approved in 2022 as F2648/F2648M – 22. DOI: 10.1520/F2648\_F2648M-23.

*1.7 This international standard was developed in accordance with internationally recognized principles on standardization established in the Decision on Principles for the Development of International Standards, Guides and Recommendations issued by the World Trade Organization Technical Barriers to Trade (TBT) Committee.*

## 2. Referenced Documents

### 2.1 ASTM Standards:<sup>2</sup>

- D618 Practice for Conditioning Plastics for Testing
- D1600 Terminology for Abbreviated Terms Relating to Plastics
- D2122 Test Method for Determining Dimensions of Thermoplastic Pipe and Fittings
- D2321 Practice for Underground Installation of Thermoplastic Pipe for Sewers and Other Gravity-Flow Applications
- D2412 Test Method for Determination of External Loading Characteristics of Plastic Pipe by Parallel-Plate Loading
- D2444 Practice for Determination of the Impact Resistance of Thermoplastic Pipe and Fittings by Means of a Tup (Falling Weight)
- D3350 Specification for Polyethylene Plastics Pipe and Fittings Materials
- D4218 Test Method for Determination of Carbon Black Content in Polyethylene Compounds by the Muffle-Furnace Technique
- D5630 Test Method for Ash Content in Plastics
- D7399 Test Method for Determination of the Amount of Polypropylene in Polypropylene/Low Density Polyethylene Mixtures Using Infrared Spectrophotometry
- F412 Terminology Relating to Plastic Piping Systems
- F449 Practice for Subsurface Installation of Corrugated Polyethylene Pipe for Agricultural Drainage or Water Table Control
- F2136 Test Method for Notched, Constant Ligament-Stress (NCLS) Test to Determine Slow-Crack-Growth Resistance of HDPE Resins or HDPE Corrugated Pipe

<sup>2</sup> For referenced ASTM standards, visit the ASTM website, [www.astm.org](http://www.astm.org), or contact ASTM Customer Service at [service@astm.org](mailto:service@astm.org). For *Annual Book of ASTM Standards* volume information, refer to the standard's Document Summary page on the ASTM website.

\*A Summary of Changes section appears at the end of this standard

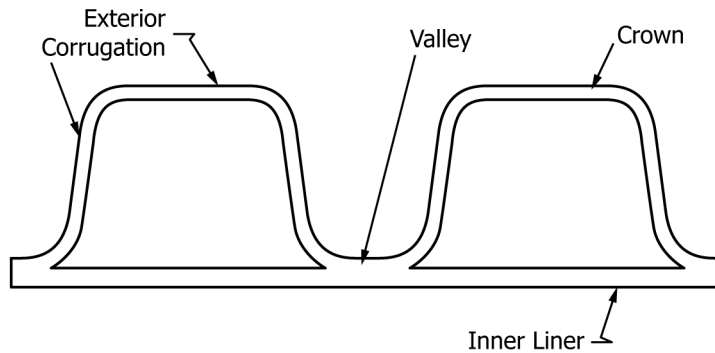


FIG. 1 Annular Corrugated Profile Wall Polyethylene Pipe with Interior Liner

TABLE 1 Pipe Dimensions and Stiffness<sup>A</sup>

| NID           |                     | Minimum Inside Diameter |       | Minimum Liner Thickness |       | Minimum Pipe Stiffness at 5% Deflection |            | Minimum SN Class |
|---------------|---------------------|-------------------------|-------|-------------------------|-------|-----------------------------------------|------------|------------------|
| Metric Series | US Customary Series | mm                      | in.   | mm                      | in.   | kPa                                     | lb/in./in. | [SN]             |
| 50            | 2                   | 48                      | 1.90  | 0.5                     | 0.020 | 345                                     | 50         | 8                |
| 75            | 3                   | 75                      | 2.97  | 0.5                     | 0.020 | 345                                     | 50         | 8                |
| 100           | 4                   | 95                      | 3.74  | 0.5                     | 0.020 | 345                                     | 50         | 8                |
| 150           | 6                   | 145                     | 5.71  | 0.5                     | 0.020 | 345                                     | 50         | 6                |
| 200           | 8                   | 195                     | 7.68  | 0.6                     | 0.024 | 345                                     | 50         | 6                |
| 225           | 9                   | 220                     | 8.66  | 0.6                     | 0.024 | 345                                     | 50         | 6                |
| 250           | 10                  | 245                     | 9.65  | 0.6                     | 0.024 | 345                                     | 50         | 6                |
| 300           | 12                  | 295                     | 11.61 | 0.9                     | 0.035 | 345                                     | 50         | 6                |
| 375           | 15                  | 369                     | 14.54 | 1.0                     | 0.040 | 290                                     | 42         | 6                |
| 400           | 16                  | 392                     | 15.43 | 1.1                     | 0.045 | 283                                     | 41         | 4                |
| 450           | 18                  | 443                     | 17.45 | 1.3                     | 0.051 | 275                                     | 40         | 4                |
| 500           | 20                  | 490                     | 19.29 | 1.4                     | 0.055 | 265                                     | 39         | 4                |
| 525           | 21                  | 517                     | 20.36 | 1.5                     | 0.060 | 260                                     | 38         | 4                |
| 600           | 24                  | 588                     | 23.15 | 1.5                     | 0.060 | 235                                     | 34         | 4                |
| 675           | 27                  | 665                     | 26.18 | 1.5                     | 0.060 | 205                                     | 30         | 4                |
| 750           | 30                  | 739                     | 29.08 | 1.5                     | 0.060 | 195                                     | 28         | 4                |
| 800           | 32                  | 785                     | 30.91 | 1.6                     | 0.063 | 180                                     | 26         | 4                |
| 900           | 36                  | 886                     | 34.90 | 1.7                     | 0.067 | 150                                     | 22         | 4                |
| 1000          | 39                  | 985                     | 38.79 | 1.8                     | 0.070 | 141                                     | 21         | 2                |
| 1050          | 42                  | 1034                    | 40.72 | 1.8                     | 0.071 | 140                                     | 20         | 2                |
| 1200          | 48                  | 1182                    | 46.54 | 1.8                     | 0.071 | 125                                     | 18         | 2                |
| 1350          | 54                  | 1330                    | 52.36 | 2.0                     | 0.079 | 110                                     | 16         | 2                |
| 1500          | 60                  | 1478                    | 58.17 | 2.0                     | 0.079 | 95                                      | 14         | 2                |

<sup>A</sup> Inside Diameters for metric (SI) sizes are in direct Imperial equivalent dimensions

2.2 AASHTO (American Association of Highway and Transportation Officials) Standard:<sup>3</sup>

(AASHTO) AASHTO LRFD Bridge Design Specifications

2.3 CSA Standards:<sup>4</sup>

B181.0 Definitions, general requirements, and methods of testing for thermoplastic nonpressure piping

2.4 NCHRP (National Cooperative Highway Research Program) Report:<sup>5</sup>

NCHRP Report 631 Updated Test and Design Methods for Thermoplastic Drainage Pipe

2.5 ISO Standard:<sup>6</sup>

ISO 15270 Guidelines for Recovery and Recycling of Plastic Waste

ISO 9969 Thermoplastics pipes —Determination of ring stiffness

### 3. Terminology

3.1 Definitions are in accordance with Terminology F412 and abbreviations are in accordance with Terminology D1600, unless otherwise specified. The abbreviation for polyethylene is PE.

3.2 Definitions of Terms Specific to This Standard:

3.2.1 buckling,  $v$ —Any reverse curvature or deformation in the pipe wall or profile element that reduces the load-carrying

<sup>3</sup> Available from American Association of State Highway and Transportation Officials (AASHTO), 444 N. Capitol St., NW, Suite 249, Washington, DC 20001, <http://www.transportation.org>.

<sup>4</sup> Available from Canadian Standards Association (CSA), 178 Rexdale Blvd., Toronto, ON M9W 1R3, Canada, <http://www.csagroup.org>.

<sup>5</sup> Transportation Research Board, The National Academies 500 Fifth Street, NW Washington, DC 20001. <http://www.TRB.org>.

<sup>6</sup> Available from International Organization for Standardization (ISO), ISO Central Secretariat, BIBC II, Chemin de Blandonnet 8, CP 401, 1214 Vernier, Geneva, Switzerland, <http://www.iso.org>.